



HAL
open science

An alternative radiolytic route for synthesizing conducting polymers in an organic solvent

Teseer Bahry, Zhenpeng Cui, Ariane Deniset-Besseau, Matthieu Gervais, Cyrille Sollogoub, Thanh-Tuân Bui, Samy Remita

► **To cite this version:**

Teseer Bahry, Zhenpeng Cui, Ariane Deniset-Besseau, Matthieu Gervais, Cyrille Sollogoub, et al.. An alternative radiolytic route for synthesizing conducting polymers in an organic solvent. *New Journal of Chemistry*, 2018, 42, pp.8704 - 8716. 10.1039/c8nj01041b . hal-02569353v1

HAL Id: hal-02569353

<https://universite-paris-saclay.hal.science/hal-02569353v1>

Submitted on 26 Sep 2023 (v1), last revised 11 May 2020 (v2)

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

An alternative radiolytic route for synthesizing conducting polymers in an organic solvent

Teseer Bahry ^a, Zhenpeng Cui ^a, Ariane Deniset-Besseau ^a, Matthieu Gervais ^b,
Cyrille Sollogoub ^b, Thanh-Tuân Bui ^c and Samy Remita ^{a, d}

^a Laboratoire de Chimie Physique, LCP, UMR 8000, CNRS, Université Paris-Sud, bâtiment 349, Campus d'Orsay, 15 avenue Jean Perrin, 91405 Orsay Cedex, France.

^b Laboratoire Procédés et Ingénierie en Mécanique et Matériaux, PIMM, ENSAM, UMR 8006, CNRS, CNAM, 151 boulevard de l'hôpital, 75013 Paris, France.

^c Laboratoire de Physicochimie des Polymères et Interfaces, LPPI, EA 2528, Université de Cergy-Pontoise, 5 mail Gay Lussac, Neuville sur Oise, 95031 Cergy-Pontoise Cedex, France.

^d Département Chimie Vivant Santé, EPN 7, Conservatoire National des Arts et Métiers, CNAM, 292 rue Saint-Martin, 75141 Paris Cedex 03, France.

Keywords: Radiolysis, Conducting polymers, PEDOT, dichloromethane

Abstract

A new and simple promising method for synthesizing conducting polymers in organic solvents was successfully achieved for the first time thanks to the oxidative polymerization of 3,4-ethylenedioxythiophene (EDOT) monomers dissolved in dichloromethane by means of gamma-radiolysis. EDOT polymerization was controlled and optimized thanks to the study of dose effect under inert atmosphere. UV-Vis absorption spectroscopy was used to follow the polymerization process and to estimate both the radiolytic yield of EDOT oxidation and the required irradiation dose for quantitative poly(3,4-ethylenedioxythiophene) (PEDOT) preparation. Size exclusion chromatography (SEC) was used to determine the molar mass of PEDOT polymers and thus their degree of polymerization. Polymers containing up to 20 EDOT units were detected. After deposition, ATR-FTIR spectroscopy and Energy-Dispersive X-ray (EDX) analysis highlighted the *in situ* doping of PEDOT polymers with chloride ions generated


during dichloromethane radiolysis, while XRD analysis demonstrated the amorphous structure of the polymers. The morphology of radiosynthesized PEDOT polymers was characterized in solution by Cryo-TEM microscopy and after deposition by SEM microscopy as well as by high-resolution AFM-IR microscopy coupled with infrared nanospectroscopy. In all cases, aggregated and packed spheroidal PEDOT particles with diameters comprised between 100 nm and 1.5 μm were observed. Besides, cyclic voltammetry (CV), four-point probe measurements and thermogravimetric analysis (TGA) showed that PEDOT polymers radiosynthesized in dichloromethane are characterized by interesting electrical properties and good thermal stability. The present study bears witness to the tremendous potential of our radiation-based methodology and gives us a glimpse of future promising syntheses of different kinds of conducting polymers in organic solvents and even in complex matrices.

1. Introduction

Studying conducting polymers (CPs) and understanding their properties is a point of interest of the scientists ^{1, 2, 3}. Organic conducting polymers such as poly(3-hexylthiophene), P3HT, and poly(3,4-ethylenedioxythiophene), PEDOT, are characterized by a backbone chain of alternating double and single bonds ⁴. The duplication of π -bonds along the polymer chain gives remarkable optical and electrical properties ^{2, 5}, leading to potential applications such as, in photovoltaic cells (OPV) ⁶, organic transistors ⁷, organic light-emitting diodes (OLEDs) ⁸, conducting materials and biological sensors ⁹.

Monomers oxidation induced polymerization, by using oxidizing species, is the way to obtain conducting polymers ^{10, 11}. The most common approaches which are used to synthesize CPs are either chemical polymerization through adding oxidizing reagents ^{11, 12} or electropolymerization by applying a potential across a solution containing the monomers ¹³. In literature, PEDOT is usually synthesized by oxidation-polymerization routes thanks to the initial oxidation of 3,4-ethylenedioxythiophene monomers (EDOT) (Scheme 1) and to the further coupling reactions in α , α' positions. Even though these two methods are well understood and their mechanism is relatively well known, still remain some problems such as chemical contamination, purification steps and sometimes need to use a catalyst. On the other hand, conducting polymers have some limitations which restrict their applications due to difficult processability, low solubility in common solvents and poor thermal stability ¹⁴.

Apart from traditional methods of polymers synthesis, ionizing radiation induced polymerization by γ -rays or accelerated electrons is not commonly used in the field of CPs synthesis¹⁵. In previous studies, our group has developed a new methodology based on radiation chemistry to polymerize some of those conducting polymers in aqueous solutions^{16, 17, 18, 19} thanks to the oxidation of dissolved organic monomers by oxidizing radicals *in situ* produced in the medium during water radiolysis. Additionally, pulse radiolysis was used to study and to understand the growth mechanism of PEDOT polymers initiated by these radicals in aqueous solution²⁰. In this way, we demonstrated that the growth of conducting polymers is not a chain reaction. In fact, it proceeds through a step-by-step recurrent oxidation process where monomers, then dimers, then oligomers are successively oxidized.

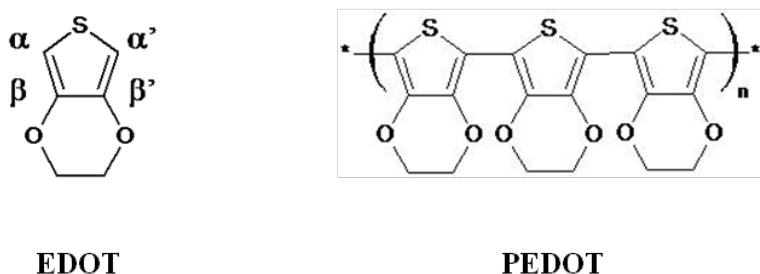

Scheme 1. Chemical structures of 3,4-ethylenedioxythiophene (EDOT) and poly(3,4-ethylenedioxythiophene) (PEDOT). EDOT structure displays the free α , α' positions where polymerization could occur.

Unfortunately, radiation-induced polymerization in aqueous solution cannot always be used due to poor processability, low solubility and even sometimes insolubility of some of concerned monomers. Contrarily to water, halo-methanes are very good solvents for many organic compounds²¹ and their gamma radiolysis has been widely studied under different conditions^{22, 23}. Moreover, γ -irradiation of halo-methane solvents yields to several oxidizing species²¹ which could enable first the oxidation of dissolved organic monomers and then their polymerization into CPs.

Among halo-methane solvents, dichloromethane (DCM), CH_2Cl_2 , has been used to carry out electrochemical or radiolytical one-electron oxidation of solutes^{21, 24}, and it has been proved that irradiated DCM is a good oxidizing system²³. Yet, to the best of our knowledge, oxidative polymerization of conducting polymers induced by gamma-irradiation of dichloromethane solutions has never been studied in literature. In this work, in order to develop a new synthetic and processable method for conducting polymers production, to control the optical properties

of radiosynthesized materials, to tune polymers morphology and to overcome the low solubility issue, we extend our methodology based on radiation chemistry through a new synthetic approach in order to polymerize EDOT in an organic solvent by exploiting the oxidizing species produced from γ -irradiation of CH_2Cl_2 (DCM).

2. Experimental section

2.1 Materials


3,4-ethylenedioxythiophene (EDOT) ($\geq 98\%$) was purchased from Sigma-Aldrich and used as a monomer. Dichloromethane (DCM) ($\geq 99.8\%$) and the other used solvents were purchased from Sigma-Aldrich. N_2 gas (Air Liquid Co.) was used to deaerate dichloromethane solutions. Nitrosyl tetrafluoroborate (NOBF_4) ($\geq 95\%$, Sigma-Aldrich) dissolved in acetonitrile ($\geq 99.9\%$, Sigma-Aldrich) was used as dopant during the electrical conductivity measurements. All compounds were used as received. Also, distilled water (Millipore system $18.2\ \Omega\cdot\text{cm}^{-1}$) and ethanol were used for washing. All experiments were performed at room temperature.

2.2 Solutions preparation and irradiation

Dichloromethane solutions containing 10 mM in EDOT monomers were prepared at ambient temperature. Note that the used concentration is lower than EDOT solubility in dichloromethane at 25°C (which is over than 20 mM as found by a UV-Vis absorption spectroscopy study (results not shown)). This concentration remains also much lower than dichloromethane molecules concentration (15.6 M). This enables one to neglect the direct effect of ionizing radiation on EDOT monomers. Dichloromethane solutions were degassed with N_2 for 20 min, sealed in glass ampoules and then irradiated with a ^{60}Co γ -source with increasing doses at a dose rate of $3.65\ \text{kGy}\cdot\text{h}^{-1}$.

2.3 Radiolysis of dichloromethane solutions and radio-synthesis of PEDOT

It is known that the oxidative polymerizations are induced by formation of cations of the monomers²⁵. This can be possible by ionizing radiation of aerated and/or deaerated solutions of DCM. It is well established that γ -irradiation of deoxygenated solutions of dichloromethane (under N_2 for instance) leads, within short nanosecond time scale, to the formation of solvated electrons in addition to neutral radicals and solvent radical cations which quickly lead to dichloromethyl (CHCl_2^\cdot) and chloromethyl ($\text{CH}_2\text{Cl}^\cdot$) radicals^{24, 26}:



All the generated radicals are well known as strong oxidizing agents towards organic materials. For instance, chlorine radicals $[\text{Cl}^\cdot/\text{Cl}^-]$ have an ionization potential of 11.48 eV²⁷, while the dichloromethane radical cations $[\text{CH}_2\text{Cl}_2^{\cdot+}/\text{CH}_2\text{Cl}_2]$ have an ionization potential of 11.35 eV²³. In addition, it has been proved the possibility of oxidation of aromatic hydrocarbons by neutral dichloromethyl and chloromethyl (CHCl_2^\cdot and $\text{CH}_2\text{Cl}^\cdot$) radicals in spite of their relatively lower redox potentials^{23, 28}. As a consequence, due to the low redox potential of EDOT²⁹, one can expect its effective radiation-induced oxidation by CHCl_2^\cdot and $\text{CH}_2\text{Cl}^\cdot$ radicals when dissolved in dichloromethane under N_2 atmosphere.

Note that, in aerated dichloromethane solutions, the produced dichloromethyl and chloromethyl radicals are rapidly scavenged by molecular oxygen (O_2) producing the corresponding peroxy radicals: $\text{CHCl}_2\text{O}_2^\cdot$ and $\text{CH}_2\text{ClO}_2^\cdot$ ^{22, 24}. Nevertheless, even if the oxidizing power of peroxy radicals is higher than that of neutral chloromethyl and dichloromethyl carbon centred radicals²⁴, we chose to work under nitrogen atmosphere in order to avoid any overoxidation of our materials in DCM.

Emmi et al. elucidated the oxidation of thiophene and oligothiophenes by means of pulse radiolysis in aerated and deaerated solutions of dichloromethane²⁶. On the other hand, Alfassi et al. calculated the total yield of oxidation of various solutes by pulse radiolysis of aerated DCM solutions²⁴. It has been shown in these latter conditions that the total yield of solutes oxidation by peroxy radicals, G_{max} , amounts to $7.77 \times 10^{-7} \text{ mol} \cdot \text{J}^{-1}$ for solute concentrations higher than 3.3 mM²⁴. Since oxidizing power of peroxy radicals generated in aerated solutions is higher than that of chloromethyl and dichloromethyl radicals formed in deaerated DCM solutions, one can deduce that the yield, G_{ox} , of solutes oxidation under N_2 atmosphere is necessarily lower than G_{max} . This should be the case for our deaerated dichloromethane solutions containing 10 mM in EDOT monomers.

The concentration of EDOT oxidized through dichloromethane radiolysis can be expressed as a function of the irradiation dose, D , expressed in Gray (Gy, 1 Gy corresponds to $1 \text{ J} \cdot \text{kg}^{-1}$) according to:

$$[\text{Oxidized EDOT}] (\text{mol} \cdot \text{L}^{-1}) = D(\text{Gy}) \times G_{\text{ox}} (\text{mol} \cdot \text{J}^{-1}) \times d (\text{kg} \cdot \text{L}^{-1}) \quad (2)$$

where G_{ox} is the effective yield of EDOT oxidation and where d is dichloromethane density ($d = 1.35 \text{ kg.L}^{-1}$).

Then, starting from equation (2) and knowing that under N_2 atmosphere, the yield of EDOT oxidation, G_{ox} , is lower than G_{max} , one can deduce that a dose higher than 10 kGy is needed for the quantitative oxidation of 10 mM in EDOT monomers dissolved in deaerated dichloromethane solutions.

As demonstrated in our previous studies ^{19, 20}, PEDOT growth is not a chain reaction but proceeds through a step-by-step oxidation mechanism made up of recurrent oxidation reactions: oxidizing radicals oxidize monomers, then dimers, then oligomers, and so on. According to this growth mechanism, the quantitative formation of PEDOT polymers requires the radiolytic production of a high concentration in oxidative species which should reach at least twice that of EDOT monomers ²⁰. This is consistent with the fact that, in a PEDOT polymer, all the monomers apart from the terminal ones, are bound to two neighbors in α and α' positions. Thus, the theoretical irradiation dose which should lead to the quantitative formation of PEDOT is twice the dose necessary for the total oxidation of EDOT monomers. In a N_2 -saturated dichloromethane solution containing 10 mM in EDOT, while the dose needed for the total oxidation of EDOT by $CHCl_2\cdot$ and $CH_2Cl\cdot$ radicals should be higher than 10 kGy, the dose which is necessary for the complete synthesis of PEDOT should be higher than 20 kGy, dependently on the effective yield, G_{ox} , of EDOT oxidation, according to:

$$D(\text{Gy}) = \frac{2[\text{EDOT}]_0(\text{mol.L}^{-1})}{G_{ox}(\text{mol.J}^{-1}) \times d(\text{kg.L}^{-1})} \quad (3)$$

where $[\text{EDOT}]_0$ is the initial concentration of EDOT.

Conversely, the determination of the dose, D , necessary for the quantitative polymerization of PEDOT should enable the estimation of the value of the yield of EDOT oxidation under nitrogen, G_{ox} , thanks to equation (3).

In this context, in order to check the dose effect and to evaluate the required irradiation dose for quantitative PEDOT preparation and then to determine the effective yield of EDOT oxidation, solutions of dichloromethane containing 10 mM in EDOT under N_2 atmosphere were irradiated at increasing doses up to 70 kGy. After irradiation, in order to extract PEDOT polymers and to evaporate the organic solvent, irradiated solutions were dried under reduced pressure. The obtained PEDOT powders were then used for further characterizations and spectral analysis.

2.4 Characterization methods

- **UV-Vis absorption spectroscopy.** UV-Vis absorption spectroscopy was used to check the optical properties of EDOT monomers and those of PEDOT polymers radiosynthesized in DCM at increasing doses. A HP 8543 spectrophotometer was used to measure the absorbance of solutions before and after irradiation. The apparatus covers wide range of wavelengths, starting from 200 nm in the UV region till 1200 nm in the near-infrared region. A quartz cell with an optical pathlength of 2 mm was used to perform all the measurements. The reference was always pure DCM solvent.
- **Attenuated Total Reflectance Fourier Transform Infrared (ATR-FTIR) spectroscopy.** FTIR was used for further chemical characterization of the polymers synthesized at increasing irradiation doses. The dried polymers were deposited on the diamond substrate of the FTIR device. The measurements were recorded by using a Bruker Vertex 70 FTIR spectrophotometer with diamond ATR attachment (PIKE MIRACLE crystal plate diamond/ZnSe) and MCT detector with liquid nitrogen cooling system. The scanning was conducted from 4000 to 600 cm^{-1} with a 4 cm^{-1} spectral resolution for 100 times and averaged for each spectrum.
- **Size exclusion chromatography (SEC).** SEC was used in order to check the average molecular weight of PEDOT polymers synthesized in dichloromethane solutions at increasing irradiation doses. Right after gamma-irradiation, 100 μL of DCM solution containing radiosynthesized PEDOT polymers were mixed with 300 μL of Tetrahydrofuran (THF) solvent and then 100 μL of the resulted mixture was injected into SEC apparatus. Using THF as eluent, SEC was performed at 40 $^{\circ}\text{C}$ on a Malvern Viscotek TDA apparatus equipped with two columns, Malvern T3000 and T6000, with a Malvern refractive index detector at an elution rate of 1 $\text{mL}\cdot\text{min}^{-1}$. Polystyrene polymers were used as standards.
- **Cryogenic-transmission electron microscopy (Cryo-TEM).** In order to check the morphology of PEDOT polymers dispersed in DCM solutions just after irradiation (irradiation dose of 36 kGy), cryo-TEM microscopy was used. The observations were carried out on a transmission electron microscope in a cryogenic environment (Cryo-TEM), known to be adapted to low density contrasts. A drop of irradiated dichloromethane solution, containing PEDOT polymers, was deposited on “quantifoil”[®] (Quantifoil Micro Tools GmbH, Germany)

200 mesh holey-carbon-coated grids. After being blotted with filter paper, the grids were quench-frozen by being rapidly plunged into liquid ethane in order to form a thin frozen dichloromethane film avoiding dichloromethane crystallization. The grids were then transferred into the microscope using a side entry Gatan 626 cryoholder cooled at $-180\text{ }^{\circ}\text{C}$ with liquid nitrogen in order to image PEDOT polymers. Images were recorded with an Ultrascan 2k CCD camera (Gatan, USA) by using a LaB6 JEOL JEM 2100 (JEOL, Japan) cryomicroscope operating at 200 kV with a low-dose system (Minimum Dose System, MDS) to protect the thin dichloromethane film from any irradiation before imaging and to reduce the irradiation during image capture. By freezing the system, Cryo-TEM ensures the observation of soft nano-objects in equilibrium in DCM solution since it avoids the phase transition and possible PEDOT aggregation resulting from drying procedures.

- **Scanning Electron Microscopy (SEM).** In order to investigate the structure of PEDOT polymers synthesized by gamma-radiolysis of DCM solvent (irradiation dose of 36 kGy) and to check their morphology after deposition, the dried polymers powder was sprinkled, after solvent evaporation, onto carbon tape adhered to aluminum mounts and then coated with gold in order to get high imaging resolution. The SEM observations were performed by using an EVO MA 10 ZEISS microscope supplied with SMRT SEM as piloting program. The functioning pressure was 105 Torr, the applied voltage was 15 kV and the scale bars were 2, 10 and 20 μm . *In situ* **Energy-Dispersive X-ray spectroscopy (EDX)** was carried out without gold coating to identify the chemical composition of the materials and to perform the elemental analysis within a selected area of the samples.

- **Atomic Force Microscopy coupled with infrared nanospectroscopy (AFM-IR).** AFM-IR was used to check whether PEDOT polymers synthesized at 36 kGy in DCM solution maintains its original morphology during the drying process. In this context, 3 mg of dried polymers powder was solubilized in 3 mL of ethanol and then a small drop of ethanolic solution was deposited onto the upper surface of ZnSe prism (transparent in the mid-IR) and dried naturally at air. The dried deposit was observed by IR nanospectroscopy. The system used here is a commercial version called nanoIRTM (@Anasys Instruments). It combines an atomic force microscope (AFM) with an infrared pulse source. The AFM is used in contact mode and the pulsed infrared laser setup covers the IR range from 4000 cm^{-1} to 1000 cm^{-1} with a repetition rate of 1 kHz and a pulse width of 10 ns. During all the measurements, the tip of the AFM remained in contact with the surface. The IR source highlights the sample from the bottom in

total internal reflexion configuration. When the sample absorbs IR laser pulse, the absorbing region warms up and a thermal expansion occurs. This rapid thermal expansion is detected by the tip in contact and causes the cantilever oscillation. As the amplitude of oscillations is proportional to the absorption, scanning the surface at a given wavenumber enables the acquisition of a chemical map of the sample, while changing the wavenumber of the IR source at a fixed position of the tip gives a local infrared spectrum.

- **X-Ray Diffraction (XRD) analysis.** XRD analysis was used to check the crystallinity of PEDOT polymers synthesized by gamma radiolysis of DCM solutions at an irradiation dose of 36 kGy. PEDOT polymers were crushed and hand-milled in order to obtain fine powders which were then used for XRD characterizations (PANalytical X'pert pro MPD with X'celerator acquisition system). The Cu K α 1 ($\lambda = 1.54059 \text{ \AA}$) radiation was used as X-ray source. A scanning rate of $0.0015 \text{ }^\circ.\text{s}^{-1}$ was employed to perform θ - 2θ scans from 10° to 80° .
- **Thermogravimetric (TGA) analysis.** Thermal stability and composition analysis of PEDOT polymers synthesized in DCM at an irradiation dose of 36 kGy were performed on a thermogravimetric analysis instrument TGA Q500 (TA Instruments, USA) under a nitrogen flow of $50 \text{ mL}.\text{min}^{-1}$. In this context, few mg of dried PEDOT polymers powder were used. The temperature ranged from 25 to $800 \text{ }^\circ\text{C}$ at a heating rate of $10 \text{ }^\circ\text{C}.\text{min}^{-1}$.
- **Cyclic-voltammetry (CV) measurements.** CV was used to investigate the electronic properties of PEDOT polymers radiosynthesized in DCM and to measure highest occupied molecular orbital (HOMO) and lowest unoccupied molecular orbital (LUMO) energy levels of these polymers. The electrochemical setup was a three-electrodes cell, with a Pt disc as working electrode, an Au wire as counter-electrode and a Pt/silver wire as pseudo-reference electrode. This latter was calibrated as recommended by IUPAC probing ferrocenium/ferrocene (Fc^+/Fc) redox potential measured at the end of each experiment. PEDOT powder obtained after an irradiation at 36 kGy and after solvent evaporation was dissolved in DCM at a concentration of $1 \text{ mg}.\text{mL}^{-1}$. Then, 1 mL of this solution was mixed into the electrochemical cell with 5 mL of acetonitrile solution containing tetrabutylammonium hexafluorophosphate (TBAPF_6) used as electrolyte at a concentration of 0.1 M. The three electrodes were then immersed into the electrochemical cell and the cyclic voltammograms were recorded at a scan rate of $20 \text{ mV}.\text{s}^{-1}$ between - 2.5 V and + 2.5 V.

- **Electrical conductivity measurements by four-point probe technique.** To measure the conductivity of PEDOT polymers synthesized in DCM solution at an irradiation dose of 36 kGy, four-point probe technique was used. PEDOT powder obtained after irradiation and solvent evaporation was dissolved in DCM at a concentration of 10 mg.mL⁻¹. The solution was then stirred for 48 h to ensure complete dispersity and homogeneity. Later, 100 μL of the solution were spin-coated on a clean glass substrate at a speed of 100 rpm for 60 s. Afterwards, the PEDOT film was rinsed and doped with NOBF₄ at a concentration of 10 mM in acetonitrile and then the substrate was placed on a hot plat and heated up at 130°C for 30 min in order to dry and evaporate the remaining solvent. A 3 Veeco Dektak 150 surface profiler was used for thickness measurement of the PEDOT film, while a Kelvin four-point probe technique was used for measuring the resistance of the film. The conductivity, ρ (S.cm⁻¹), was determined thanks to the following equation:

$$\rho = \left(\frac{\pi}{\ln 2} \times \frac{V}{I} \times t \right)^{-1} \quad (4)$$

where V is the voltage difference (V), t the film thickness (cm) and I the applied current (A).

3. Results and Discussion

3.1 Radiation induced synthesis of PEDOT and dose effect study

A dichloromethane solution containing 10 mM in EDOT was prepared under N₂ and its UV-vis absorption spectrum was recorded before irradiation (insert of Figure 1a). As observed, the prepared EDOT solution exhibits two absorption maxima at 242 and 259 nm which are features of π-π* electronic transitions in the thiophene rings within dichloromethane solvent¹⁶. This is consistent with the fact that pure thiophene molecules absorb light in the UV region between 225 and 245 nm, this absorption being ascribed to π-π* transition³⁰. Within this context, EDOT showed good solubility in dichloromethane which is higher than 20 mM (results not shown). Also, at the two absorption maxima, the extinction coefficients of EDOT were found to be ε₂₄₂ = 4747 and ε₂₅₉ = 6020 L.mol⁻¹.cm⁻¹.

As elucidated in our previous work¹⁵, knowing the extinction coefficients of EDOT, one can deduce the initial radiolytic yield of EDOT consumption from the variation of EDOT concentration as a function of the irradiation dose. Nevertheless, in the present work, it was impossible to follow up the decrease in EDOT absorption since from the beginning of the irradiation, even at lower doses, radiolytic products appeared to also absorb in the UV region

of the spectrum (results not shown). These products could come either from EDOT oxidation or from the radiolysis of dichloromethane solvent. Indeed, it has been demonstrated in literature that the products of dichloromethane radiolysis in an oxygen-free atmosphere, namely (1,1-dichloroethane, 1,2-dichloroethane, 1,1,2-trichloroethane and 1,1,2,2-tetrachloroethane), absorb light between 230 and 400 nm³¹. This evidently prevents the direct study of EDOT decay. Nevertheless, detecting the formation of PEDOT polymers by following their UV-Vis absorption spectra as a function of the dose should allow us to estimate the approximate irradiation dose needed to achieve the complete oxidative polymerization of EDOT monomers into PEDOT polymers in dichloromethane solution.

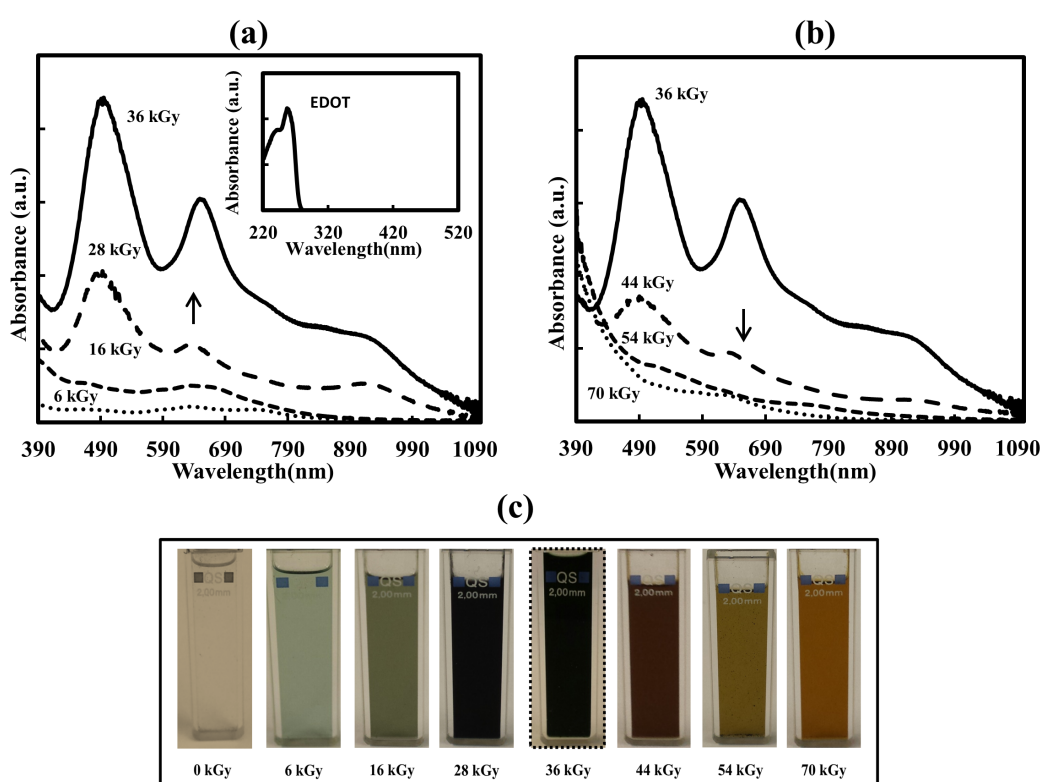


Figure 1. UV-Vis absorption spectra of DCM solutions containing 10 mM in EDOT and irradiated under N_2 atmosphere at increasing doses from: (a) 0 to 36 kGy and (b) from 36 to 70 kGy. The reference was DCM. (c) Photographs of DCM solutions before and after irradiation at increasing doses.

In order to follow the progressive formation of PEDOT polymers, dichloromethane solution containing 10 mM in EDOT was irradiated under N_2 at increasing doses up to 70 kGy (Figure 1c) and its absorption spectrum was recorded as a function of the irradiation dose

(Figure 1a and 1b). Up to an irradiation dose of 36 kGy, progressively and remarkably, two peaks were being protruded at 490 and 650 nm (Figure 1a). These peaks can be attributed to the radiation induced formation of PEDOT polymers. Indeed, it's worth noting that PEDOT polymers usually display, in solution, characteristic peaks at approximately 400 to 700 nm which are ascribed to the π - π^* transitions along the polymer chains^{32, 33}. Differently, the observed large absorption band which progressively grows up between 800 and 1000 nm can be attributed to polaron and/or bipolaron bands, which are characteristic of oxidized state of PEDOT^{34, 35}. This will be proved later in the manuscript, moreover. As far as we can say that the considerable amount of hydrochloride acid produced from γ -irradiation of dichloromethane, yields to different doping states of PEDOT. As a consequence, the doped PEDOT polymers with chloride ions show an absorption maximum at approximately 900 nm corresponding to the charge carrier band of the charged polymers³⁵. Note that proceeding the solutions with irradiation doses higher than 36 kGy leads to gradual decrease in the absorption of PEDOT polymers at 490 and 650 nm (Figure 1b).

Dichloromethane solution containing 10 mM in EDOT appears colorless before irradiation (Figure 1c). Nevertheless, γ -radiolysis induces a progressive change in the color of the solution. After 6 kGy-irradiation, the solution got a sky-blue color. This color darkened with proceeding the irradiation with higher doses up to 36 kGy. Dark blue and black precipitants were systematically observed in solutions irradiated at doses comprised between 28 and 36 kGy. However, when exceeding the dose of 36 kGy and continuing the irradiation up to 70 kGy, the solution gradated toward brown, then yellow and finally orange, while the black precipitant appeared to be glue. These color fluctuations above 36 kGy and the spectral variations upon using overdose, are ascribed to the overoxidation of PEDOT polymers (as it will be demonstrated by ATR-FTIR spectroscopy and SEC chromatography), which evidently leads to degradation and breaking down of the polymer chains.

Size exclusion chromatography (SEC) was used to check the appearance of oligomeric structures synthesized in DCM solutions at increasing irradiation doses (Figure 2). The molar masses, M_p , at the maxima of the peaks were measured as the calculation of the average molecular weights, M_n , may be influenced by the overlapping of the different peaks. The more intense peak, peak (a), around the molar mass of 1100 g.mol⁻¹ (obtained with a polystyrene calibration), which corresponds to 8 EDOT units, was observed as soon as the irradiation dose is equal or above 16 kGy (elution times between 19.5 and 21 min.). The molar masses, M_p , at this peak are reported in insert of Figure 2. When increasing the dose, one can observe an enlargement and a slight shift of peak (a) to shorter elution times, meaning that the molecular

weight slightly increases with the dose. Polymers with higher molecular weight (up to 20 EDOT units were also detected from 36 kGy). Nevertheless, even if longer polymers are obtained at higher irradiation doses, more and more oligomers of lower molecular weight (elution times between 21 and 21.5, peak (b)) are formed at doses above 36 kGy, indicating the occurrence of damages and breaking down of the polymer chains. As it will be later demonstrated thanks to ATR-FTIR spectroscopy, these polymers which were exposed to overdoses exhibit absorption peaks corresponding to overoxidized state.

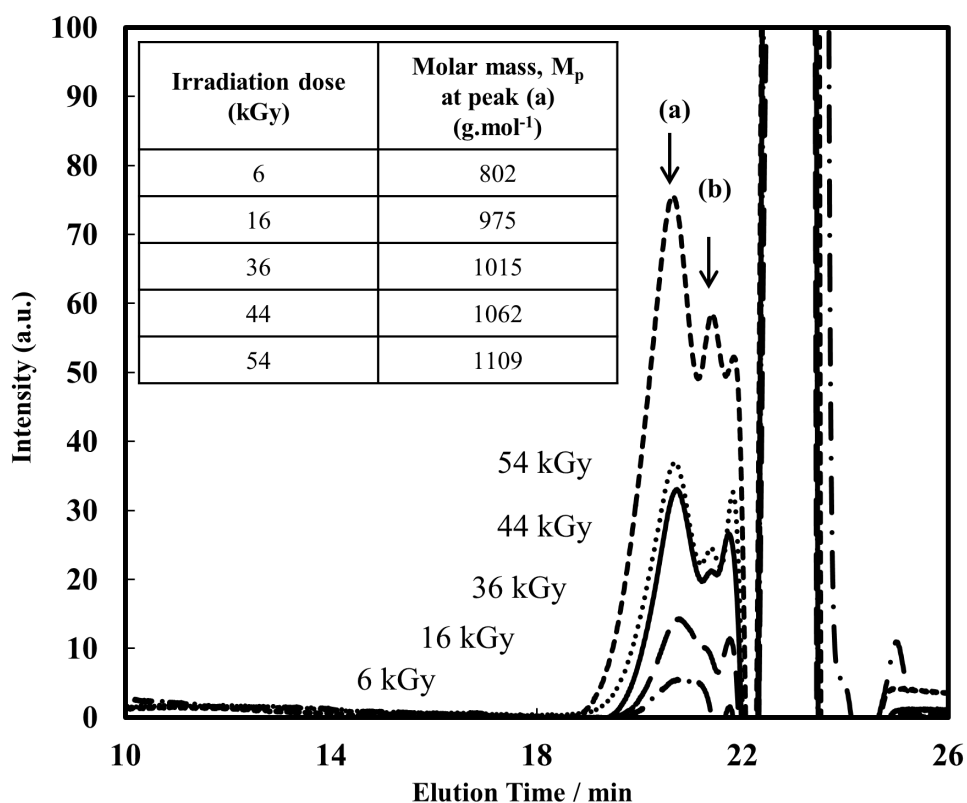


Figure 2. SEC chromatograms of PEDOT polymers synthesized in DCM under N_2 by γ -radiolysis at increasing doses. The initial concentration of EDOT was 10 mM.

Subsequently, these findings suggest that the oxidative polymerization of EDOT (10 mM) in dichloromethane can be proceeded with an irradiation dose of 36 kGy. This dose can be considered as the dose, D , necessary for the quantitative production of PEDOT starting from 10 mM in EDOT. From equation (3), one can then estimate the value of the effective yield of EDOT oxidation under nitrogen: $G_{\text{ox}} = 4.12 \times 10^{-7} \text{ mol}\cdot\text{J}^{-1}$. It is clear that, under our experimental conditions under N_2 , the radiation induced oxidative polymerization of EDOT can be initiated by the generated oxidizing species in dichloromethane. As expected, the yield of

oxidation, G_{ox} , is lower than G_{max} ($7.77 \times 10^{-7} \text{ mol.J}^{-1}$) since chloromethyl and dichloromethyl radicals are less oxidant than peroxy radicals.

Attenuated total reflectance Fourier transform infrared spectroscopy (ATR-FTIR) was used to assert the successful formation of PEDOT polymers and also to verify the oxidative polymerization in dichloromethane solutions at different doses. After irradiation, in order to get pure PEDOT polymers, samples were dried under reduced pressure enabling DCM evaporation and EDOT monomer residues elimination. In case of solutions irradiated at 16 and 36 kGy, solvent removal led to dark solid powders while in case of sample irradiated at 54 kGy, drying process led to a glutinous product. The dried compounds were then characterized by ATR-FTIR spectroscopy and their spectra were compared with that of pure non-irradiated EDOT within wavenumber region from 3600 to 600 cm^{-1} (Figure 3). Note that the difference between the intensity of polymers spectra and that of EDOT spectrum results from the types of deposition on the ATR-FTIR crystal. The deposition of EDOT liquid phase is translated by a better resolution when compared with the solid phase deposition of polymers.

As observed on Figure 3, infrared spectra of EDOT and PEDOT (whatever the irradiation dose) are in good agreement with earlier reports. The vibration bands at 1213, 1130 and 1052 cm^{-1} are attributed to stretching of the C-O-C bond in the ethylenedioxy group, peak at 933 cm^{-1} is ascribed to the ethylenedioxy ring deformation mode³⁶. Also, the vibration modes of the C-S bond which is present in the thiophene ring can be observed at 848 and 817 cm^{-1} ^{33, 36}. One can note also, as highlighted in EDOT spectrum, absorption bands located at 1365, 1436 and 1481 cm^{-1} which can be assigned to C-C and C=C bonds. More interestingly, the infrared spectrum of pure EDOT displays typical bands at 754, 890 and 1185 cm^{-1} , attributed to the =C-H in-plane and out-of-plane deformation vibrations of pure EDOT^{15, 36, 37}, which are not observed in the spectra of PEDOT. The absence of these bands after irradiation implies the formation of PEDOT polymers thanks to α, α' -coupling reactions¹⁶.

The infrared spectra obtained after irradiation reveal the typical bands of PEDOT polymers. Nevertheless, one can note the presence, whatever the irradiation dose, of a less common infrared band located at 1640 cm^{-1} . This band has already been observed in earlier works in the case of PEDOT polymers doped with chloride ions^{38, 35}. The presence of this band highlights the doping state of PEDOT for all irradiation doses³⁵ and is in full agreement with the results obtained by UV-vis absorption spectroscopy (absorption band at 900 nm). This peak originates from the quinoidal structure of thiophene ring^{33, 39}. Remarkably, this peak resulting from polymers doping has never been observed in our previous works about radiation induced synthesis of PEDOT in aqueous media¹⁵. Note the absence in the infrared spectra obtained after

irradiation of the strong band of C-Cl bond which should appear between 600 and 700 cm^{-1} . This means that no chlorine atom is covalently bonded to PEDOT polymers chains.

When comparing the absorption spectra of PEDOT on Figure 3, one can observe the specific presence, in case of an irradiation dose of 54 kGy, of a broad band from 1650 to 1730 cm^{-1} which is the sign of an overoxidation state⁴⁰. That band could be attributed to the formation of carbonyl group (C=O). At 54 kGy, one can also clearly observe two intense bands at 1080 and 1255 cm^{-1} ascribed to the symmetric and antisymmetric vibrations from the sulfone groups in the thiophene units as reported in literature concerning PEDOT overoxidation⁴⁰.

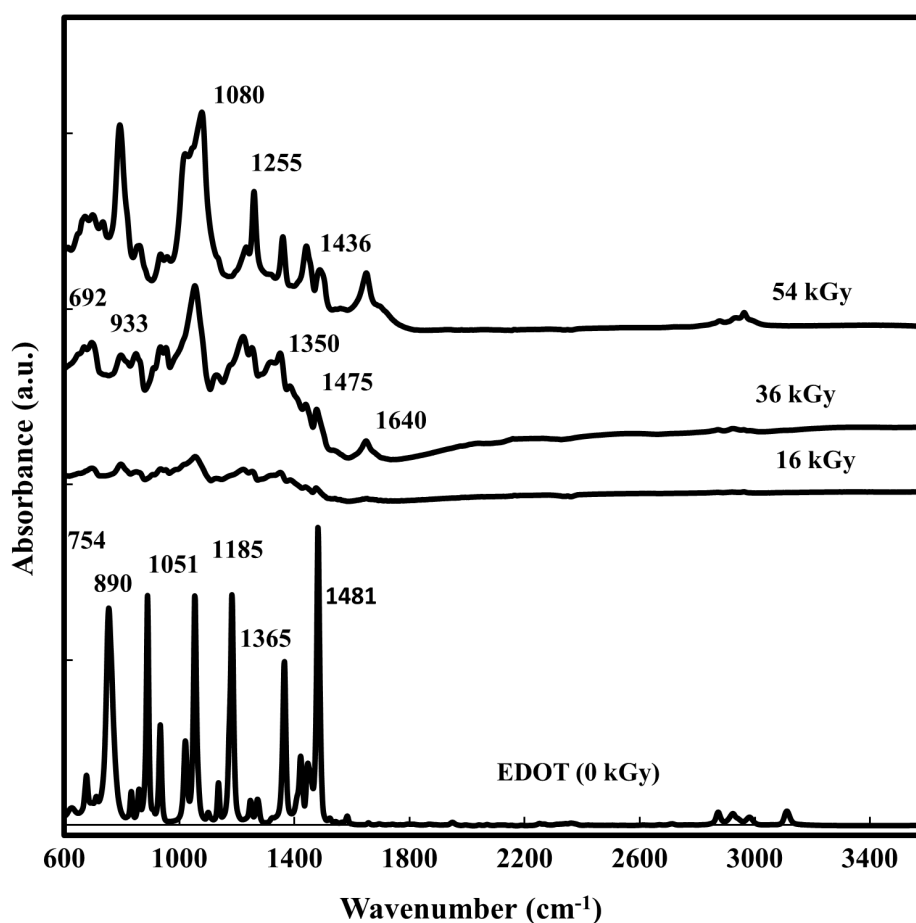


Figure 3. ATR-FTIR spectra of pure EDOT monomers and of PEDOT polymers radiolytically synthesized in DCM solvent in presence of 10 mM in EDOT at irradiation doses of 16, 36 and 54 kGy under N_2 atmosphere.

The study by UV-vis absorption spectrophotometry and by ATR-FTIR spectroscopy of the dose effect enables us to claim that we succeeded in the radiation induced synthesis of PEDOT polymers in DCM under N_2 atmosphere. Whatever the irradiation dose, the polymers are found

doped with chloride anions generated in the medium through dichloromethane radiolysis. As demonstrated by UV-vis absorption spectrophotometry, ATR-FTIR spectroscopy and SEC chromatography, 36 kGy is the optimal irradiation dose which enables quantitative polymerization of EDOT. Above this irradiation dose, an overoxidation is systematically observed, which leads to degradation and breaking down of PEDOT polymer chains.

3.2 Structural and morphological characterizations of radiosynthesized PEDOT

From now, the manuscript will focus on the characterization of PEDOT polymers produced under N_2 from DCM radiolysis at the optimal irradiation dose of 36 kGy.

In order to check the morphology of PEDOT polymers synthesized under N_2 atmosphere in a dichloromethane solution containing 10 mM in EDOT, cryo-TEM microscopy was used just after a 36 kGy-irradiation and before any sedimentation (Figure 4). Thanks to sample freezing, this technique enables *in situ* observation, into dichloromethane solvent, of radiosynthesized polymers, avoiding any phase transition and any PEDOT aggregation which could result from drying procedures.

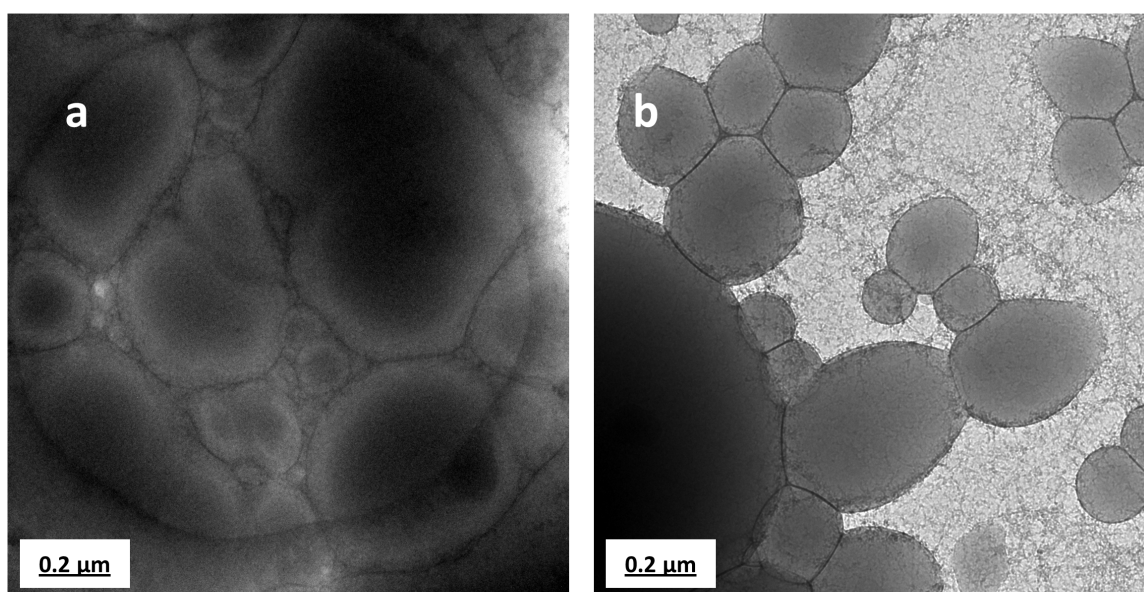


Figure 4. Cryo-TEM images of PEDOT polymers self-assembled in DCM solvent right after a 36 kGy-irradiation. The polymers were synthesized under N_2 atmosphere in DCM solvent in presence of 10 mM in EDOT.

Figure 4a displays a zoom of one of the circular holes of the holey-carbon grid coated with PEDOT polymers in DCM solvent. As depicted in the figure, this hole is fully coated with more

or less spherical contrasted objects. As explained and demonstrated in our previous works, these globular structures correspond to self-assemblies of independent amorphous PEDOT chain polymers. The full coverage of the hole and the packing of the spheroidal PEDOT particles traduces the high local concentration of these PEDOT self-assemblies into the holes of the carbon grid. In the vicinity of the holes (Figure 4b), concentration of PEDOT particles clearly appears lower due to the smaller thickness of the frozen sample outside the holes, enabling the clear observation of individual spheroidal PEDOT particles which nevertheless remain packed. PEDOT particles are heterogeneous in size with diameters comprised between 100 nm and 1 μm . Each observed particle should be composed of interdigitated polymer chains. Since no α - β' linkages could occur during polymerization, radiosynthesized PEDOT should be composed of linear chain polymers which are neither branched nor networked but in weak interactions.

After irradiation, samples were dried under reduced pressure, DCM solvent was evaporated and black PEDOT powder was extracted and collected for further characterizations. XRD analysis was then used to check the crystallinity of PEDOT polymers synthesized by gamma-radiolysis of DCM solutions. In particular, powder X-ray diffraction pattern was studied in order to analyze the structure of PEDOT polymers synthesized at 36 kGy (Figure 5).

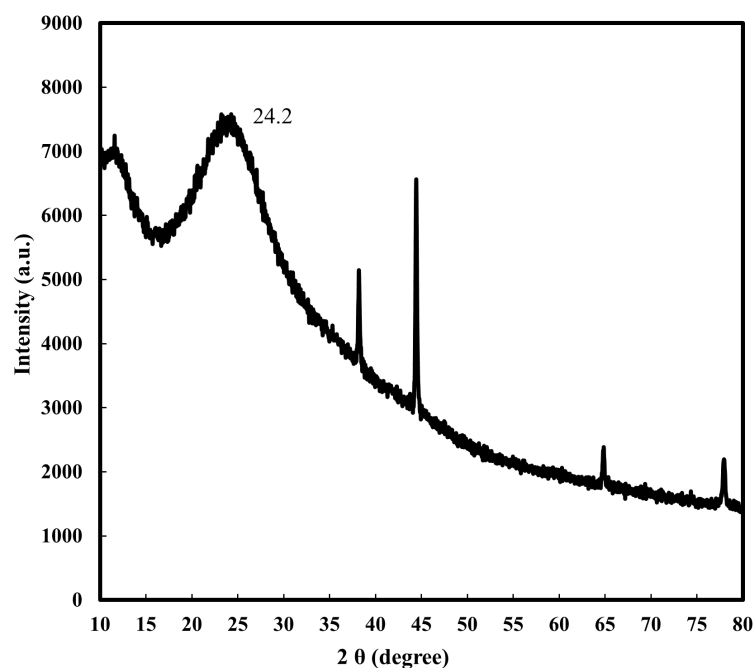


Figure 5. XRD pattern of dried PEDOT polymers powder obtained after DCM evaporation. The polymers were synthesized by gamma-radiolysis at 36 kGy of a DCM solution containing 10 mM in EDOT under N_2 atmosphere. The substrate used for XRD analysis was aluminium.

The typical XRD pattern exhibited in Figure 5 in the case of radiosynthesized PEDOT closely matches those earlier reported in literature in the case of chemically synthesized PEDOT polymers^{41, 42}. The diffraction peaks at about 38°, 44°, 64° and 78° are originated from the aluminum support used in this work. More interestingly, the amorphous nature of PEDOT is highlighted and confirmed from the diffraction peak at $2\theta \sim 24^\circ$ which is a feature of interchain planar ring stacking^{42, 43}.

In order to investigate the morphology of PEDOT polymers powders obtained after a 36 kGy irradiation of an EDOT-containing DCM solution and after solvent evaporation, SEM microscopy was used. SEM images recorded after deposition of dried PEDOT polymers powder onto carbon tape adhered to aluminum mounts and gold coating are displayed on Figure 6. Note that without gold coating, similar images were obtained but with lower resolution. SEM image of Figure 6a displays a comprehensive view of creased film of PEDOT. Without gold coating, *in situ* Energy-Dispersive X-ray spectroscopy (EDX) was carried out in order to identify the chemical composition of the materials and to perform the elemental analysis in different areas of the film. EDX highlighted the presence of sulfur (in addition to carbon and oxygen) in the whole sample demonstrating that the film is effectively made of PEDOT. Moreover, EDX enabled the detection of chlorine atoms homogeneously dispersed in the film. This observation definitely demonstrates that radiosynthesized PEDOT are doped with chloride ions, in total agreement with our results obtained by UV-vis absorption spectrophotometry and by ATR-FTIR spectroscopy.

Figure 6b which shows a closer view of PEDOT film, highlights the presence of aggregated spheroidal particles at its surface. These packed globular particles can be clearly seen in Figure 6c (first zoom of Figure 6b). These PEDOT particles have a mean diameter of few hundreds nm. Another zoom of the film (Figure 6d, second zoom of Figure 6b, which was realized in a region of Figure 6b where no apparent particles were observable) depicts the presence of bigger spheroidal PEDOT particles with a mean diameter between 1 and 1.5 μm . This means that the whole film is made of very close-packed PEDOT nanoparticles. These results are in good agreement with previous observations reported in literature concerning PEDOT films prepared by electrochemical method and doped with Cl³⁸.

Interestingly, as observed by SEM microscopy, PEDOT particles are heterogeneous in size with diameters comprised between 100 nm and 1.5 μm . This is in agreement with cryo-TEM observations. Then the particles observed by SEM after deposition should come from the globular structures initially dispersed in DCM solvent and already observed by cryo-TEM (Figure 4). The drying process as well as the deposition procedure have clearly no effect on the

size of the particles nor on their shape. This would imply the existence of relatively strong interactions (π -stacking and/or hydrogen-bonds interaction) into each polymers particle.

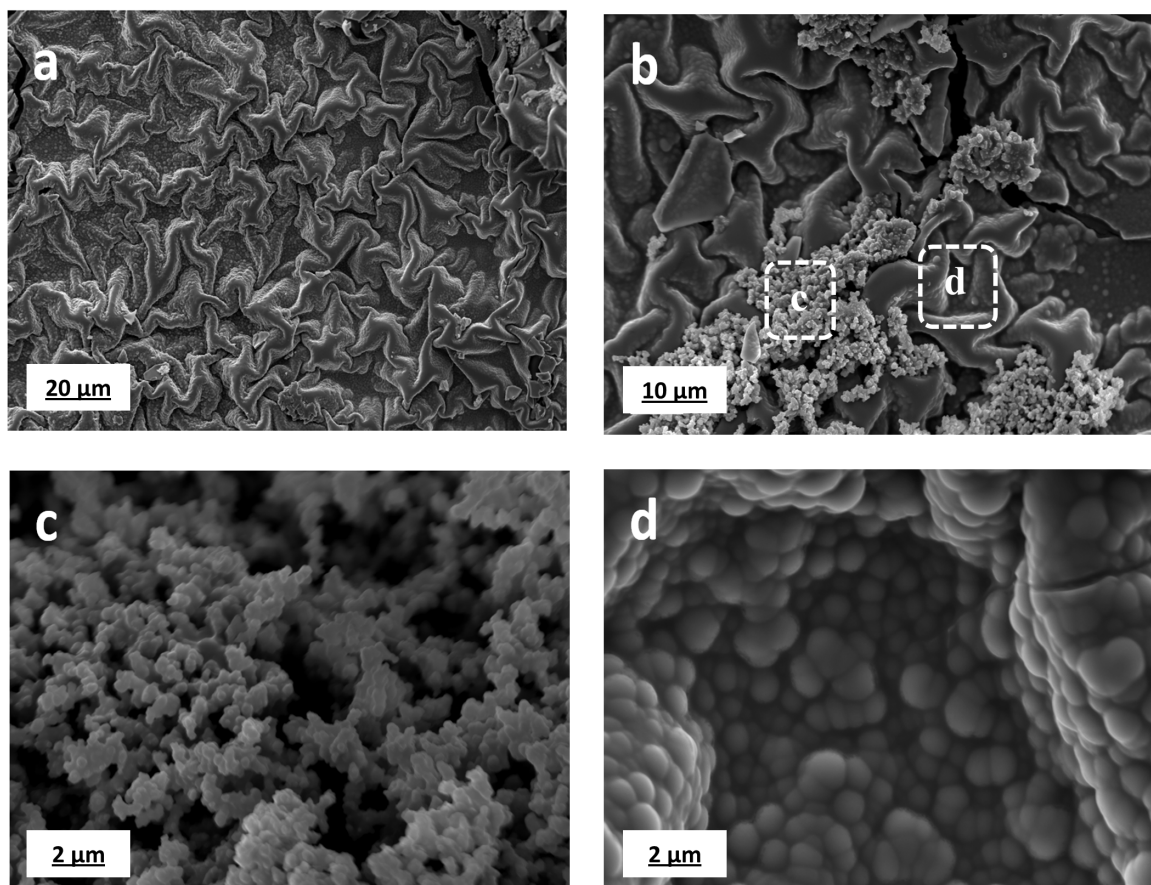


Figure 6. SEM images of dried PEDOT polymers powder after deposition onto carbon tape adhered to aluminum mounts and gold coating. The powder was obtained after solvent evaporation. PEDOT polymers were synthesized by gamma-radiolysis at 36 kGy of a DCM solution containing 10 mM in EDOT under N_2 atmosphere.

For further characterization and to definitely prove that the spheroidal particles observed by cryo-TEM and SEM are made of PEDOT polymers, Atomic Force Microscopy coupled with infrared nanospectroscopy (AFM-IR) was used. PEDOT polymers powder obtained after irradiation at 36 kGy and after DCM evaporation was solubilized in ethanol and then a small drop of the ethanolic solution was deposited onto the upper surface of ZnSe prism and dried naturally at air. The obtained film was then scanned and imaged by AFM-IR as shown in Figure 7.

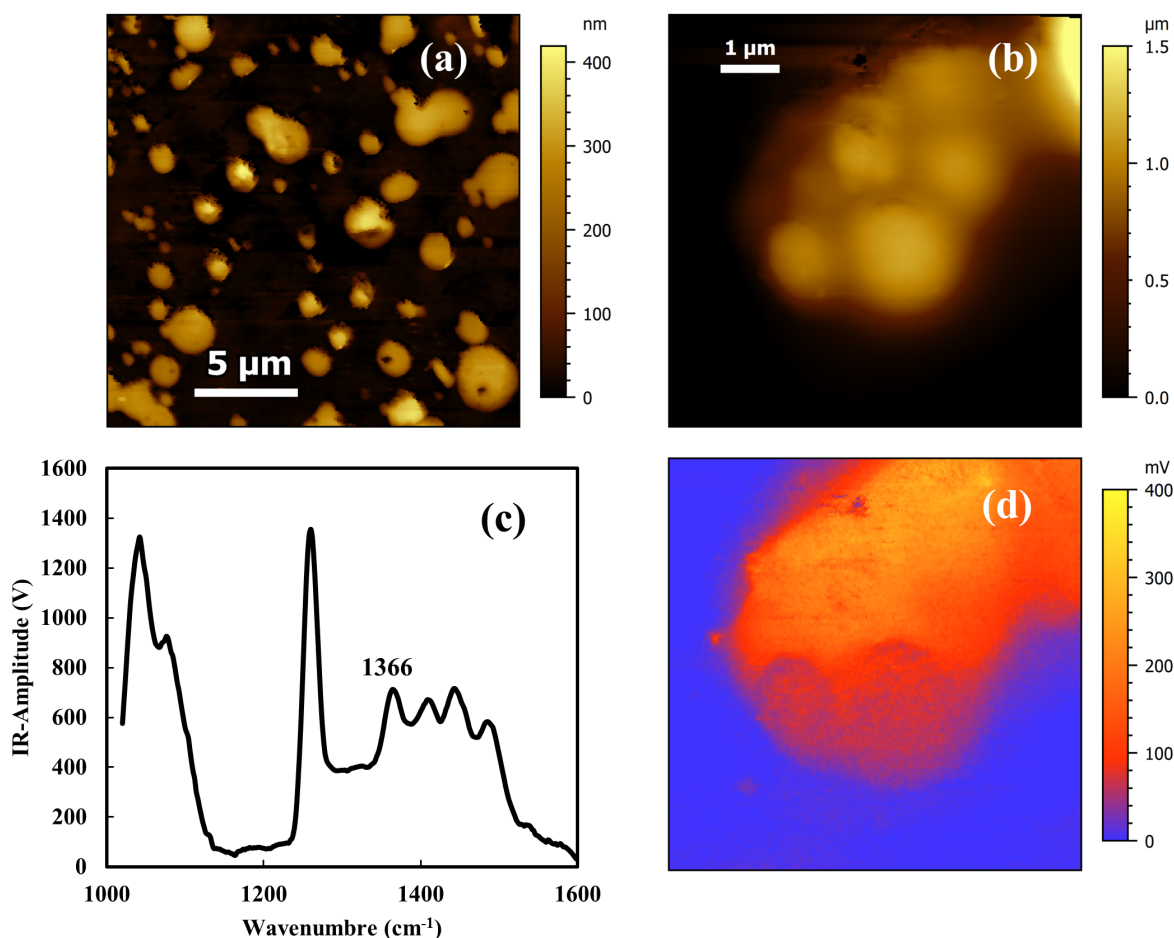


Figure 7. AFM-IR images of PEDOT polymers after deposition onto the upper surface of ZnSe prism. PEDOT polymers were synthesized by gamma-radiolysis at 36 kGy of a DCM solution containing 10 mM in EDOT under N_2 atmosphere. **(a)** and **(b)** AFM topographic images of PEDOT polymers in contact mode. **(c)** AFM-IR spectrum of PEDOT. **(d)** AFM-IR chemical mapping of PEDOT with the IR source tuned to the C-C band at 1366 cm^{-1} .

In Figure 7a and Figure 7b, the bottom dark areas having no thickness correspond to the prism. Distinctly, the topography of the deposited materials displayed as the bright areas corresponds to the thicker regions made up of more or less aggregated spheroidal particles. The AFM topography image in Figure 7a recorded in contact mode reveals the presence of big particles with diameters comprised between 0,5 and 3,5 μm . Nevertheless, if we spot on one of these big particles as shown in Figure 7b, it is possible to observe that the apparently big spheroidal particle is constructed by smaller aggregated particles. By scanning the whole substrate, we found that the smallest identifiable particles are heterogeneous in size with diameters comprised between 100 nm and 1.5 μm . The particles observed by AFM have then

the same size as the particles we already observed by cryo-TEM and SEM, those we previously considered as radiosynthesized PEDOT particles.

In order to definitely demonstrate that these particles and then those previously observed by SEM and cryo-TEM are made of PEDOT, we performed AFM-IR experiments. Indeed, changing by AFM-IR the wavenumber on a fixed position of the tip gives a local infrared spectrum. Thanks to AFM-IR, we recorded the local infrared absorption spectrum of the particles observed in Figure 7b in the range of 1020-1600 cm^{-1} (Figure 7c). Note that all the particles observed by AFM onto the prism display the same infrared spectrum, which means that they all have the same chemical structure. The infrared spectrum of Figure 7c matches with the ATR-FTIR spectra recorded in the case of PEDOT radiosynthesized at different irradiation doses (16, 36 and 54 kGy, Figure 3). This proves that the spheroidal particles observed by AFM (and thus by SEM and cryo-TEM) contain close-packed PEDOT polymer chains.

Now, scanning the surface by AFM-IR at a given wavenumber enables to reveal the chemical map of the sample. We considered in particular, in the spectrum of Figure 7c, the peak at 1366 cm^{-1} which is a feature of C-C stretching band in PEDOT, we selected the corresponding wavenumber to carry out the chemical mapping of the sample and we recorded the absorption strength (Figure 7d). In this figure, the orange-red areas indicate a stronger absorption at the characteristic wavenumber which is caused by a thick layer of PEDOT linked onto the ZnSe prism. When comparing the topography (Figure 7b) and the chemical mapping (Figure 7d), one can observe that the stronger absorbing areas fit well with the thicker regions. This implies that the observed particles are mainly composed by PEDOT polymer chains.

The observations made by cryo-TEM, SEM and AFM microscopies as well as the characterizations conducted by XRD analysis, EDX spectroscopy and AFM-IR nanospectroscopy enable us to conclude without any ambiguity that radiolysis of DCM leads to the oxidation of EDOT monomers and to the production of amorphous PEDOT polymers doped with chloride ions. As observed in the case of a 36 kGy-irradiation, radiosynthesized PEDOT polymers self-assemble into polydisperse globular particles (diameters comprised between 100 nm and 1.5 μm), those we observed in this work by cryo-TEM, SEM and AFM-IR.

3.3 Physicochemical and Electrochemical performances of radiosynthesized PEDOT

Thermogravimetric analysis (TGA) was used in order to check the thermal stability of PEDOT polymers synthesized by radiolysis under N_2 atmosphere in a dichloromethane solution

containing 10 mM in EDOT. The TGA profile obtained in the case of PEDOT polymers radiosynthesized at an irradiation dose of 36 kGy is displayed in Figure 8.

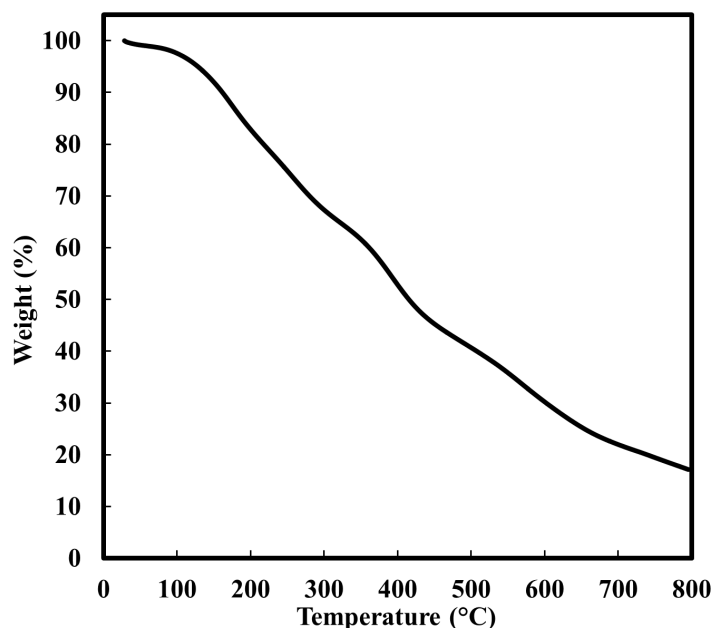


Figure 8. Thermogravimetric analysis (TGA) graph of dried PEDOT polymers powder. The polymers were synthesized by gamma-radiolysis at 36 kGy of a DCM solution containing 10 mM in EDOT under N_2 atmosphere.

As observed in Figure 8, TGA curve exhibits the typical decomposition behavior of PEDOT polymers synthesized by traditional methods^{37, 42}. Before 100°C, no weight loss is observed. However, above 150°C, a more or less progressive weight loss happens resulting from PEDOT fragmentation and carbon oxidation. It can be clearly observed two pronounced falls which occur between 150°C and 450°C. The first weight loss observed between 150°C and 300°C should correspond to the degradation of the shortest PEDOT oligomers with relatively low molecular weight, while the second weight loss observed above 300°C should correspond to the decomposition of longer polymers. This TGA analysis of radiosynthesized PEDOT is in very good agreement with TGA data already reported in the literature concerning PEDOT polymers produced by conventional methodologies^{37, 42}. This result evidently highlights the good thermal stability of PEDOT polymers synthesized by gamma-radiolysis in DCM solvent.

In order to investigate the electronic properties of PEDOT polymers radiosynthesized in DCM for future applications in optoelectronics and electrocatalysis, it is evidently necessary to

determine by using cyclic voltammetry (CV) measurements their oxidation and reduction potentials and then to estimate the energy level of the highest occupied molecular orbital (HOMO) from the ionization potential, the energy level of the lowest unoccupied molecular orbital (LUMO) from the electronic affinity, as well as the band gap.

Cyclic voltammetry (CV) was then used to study the electrochemical behavior of PEDOT polymers synthesized by radiolysis at 36 kGy in a dichloromethane solution containing 10 mM in EDOT under N_2 atmosphere. PEDOT powder obtained after solvent evaporation was dissolved in DCM at a concentration of $1 \text{ mg}\cdot\text{mL}^{-1}$. Then, 1 mL of this solution was mixed with 5 mL of acetonitrile solution containing tetrabutylammonium hexafluorophosphate ($TBAPF_6$) used as electrolyte at a concentration of 0.1 M. The electrochemical behavior of PEDOT polymers and their characteristic oxidation and reduction peaks are presented in Figure 9.

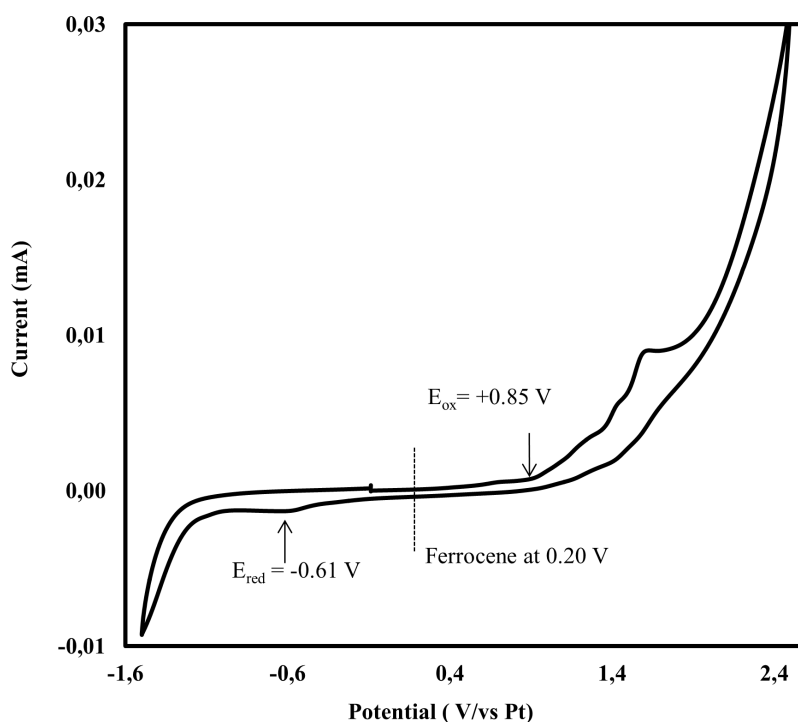


Figure 9. Cyclic voltammogram of PEDOT polymers recorded in acetonitrile containing 0.1 M of $TBAPF_6$ at a scan rate of 20 mV/s. PEDOT polymers were radiosynthesized at 36 kGy in a DCM solution containing 10 mM in EDOT under N_2 atmosphere. Ferrocenium/ferrocene (Fc^+/Fc) redox potential was measured in order to calibrate the pseudo reference electrode (0.2 V vs. Pt in the present study). The HOMO/LUMO energetic levels of PEDOT are determined as follows: E_{HOMO} (eV) from ionization potential = $-4.8-e$ ($E_{ox}-0.2$) and E_{LUMO} (eV) from electronic affinity = $-4.8-e$ ($E_{red}-0.2$) where e is the elementary charge.

The several peaks which are clearly observed from the sinuous cyclic voltammogram of Figure 9 could be assigned to the polydispersity in size of the PEDOT oligomers and polymers which are present in the electrochemical cell. According to CV profile displayed in Figure 9, main PEDOT p-doping (oxidation) process occurs at onset potential, E_{ox} , of + 0.85 V while n-doping starts at onset potential, E_{red} , of -0.61 V. Knowing these two potential values, one can calculate, from the equations given in legend of Figure 9, the HOMO/LUMO energy levels of radiosynthesized PEDOT: E_{HOMO} and E_{LUMO} amount respectively to -5.45 eV and -3.84 eV. The HOMO/LUMO energy levels of the material are calculated by using the ferrocene ionization potential value as the standard. The corrected value of 4.8 eV vs vacuum of ferrocene is widely adopted. This value is based on the calculations obtained by Pommerehne et al.⁴⁴. As a consequence, the corresponding electrochemical band gap is -1.61 eV. Note that the optical band gap deduced from the UV-Vis absorption spectrum of PEDOT irradiated at 36 kGy (Figure 1a, at $\lambda = 750$ nm) amounts to -1.65 eV. We can notice the similarity between the two estimated values of the band gap and also the good agreement with results earlier reported in literature for PEDOT polymers synthesized by conventional methods^{42, 45}.

Eventually, four-point probe technique was used to measure the electrical conductivity of PEDOT polymers synthesized by radiolysis at 36 kGy in a dichloromethane solution containing 10 mM in EDOT under N_2 atmosphere. PEDOT powder obtained after irradiation and solvent evaporation was dissolved in DCM at a concentration of 10 mg.mL⁻¹. Then, 100 μ L of the solution were spin-coated on a clean glass substrate and the obtained PEDOT film was doped with NOBF₄ (10 mM) in acetonitrile. After measuring the thickness of the film by a surface profiler, its conductivity was determined by four-point probe technique and found to be 2.6×10^{-3} S.cm⁻¹. The conductivity of PEDOT polymers synthesized by radiolysis in DCM is then close to the conductivities of PEDOT polymers we earlier synthesized by high energy radiation (gamma-rays or accelerated electrons) in aqueous solution^{18, 20} and remains close to those already reported in literature for PEDOT polymers produced by conventional synthetic methods^{36, 46}.

The measurements and characterizations made by thermogravimetric analysis, cyclic voltammetry and four-point probe technique enable us to conclude that PEDOT polymers synthesized in dichloromethane by our alternative radiolytic method have not only a good thermal stability but also present interesting electronic properties (band gap and conductivity), which are comparable to those reported in literature for PEDOT polymers synthesized by

chemical or electrochemical methodologies. Thus, the obtained data are really promising and surely usable for practical applications.

4. Conclusion

Recently and for the first time in literature, radiolysis (by γ -rays or accelerated electrons) was used in the host laboratory as a new methodology for the synthesis of conducting polymers in aqueous solution in the absence of any external chemical initiators. Oxidation of monomers was shown to result from the action of oxidizing radicals *in situ* produced by water radiolysis while growth of polymers was shown to proceed through a recurrent step-by-step oxidation process. Starting from Py and EDOT monomers, nanostructured conducting PPy and PEDOT polymers were then successfully prepared. Nevertheless, high energy radiation induced polymerization cannot systematically be used in aqueous solution due to poor solubility into water and even sometimes insolubility of monomers.

Herein, our strategy based on radiation chemistry was extended to the preparation of conducting polymers into organic solvents. In particular, starting from EDOT monomers dissolved in dichloromethane (DCM) solvent, we elaborated and optimized the synthesis by gamma-rays of PEDOT polymers. The choice of DCM was justified by the fact that it is a good solvent for many organic compounds. Moreover, its radiolysis is relatively well-known and leads to *in situ* production of oxidizing radicals which should enable first the oxidation of dissolved organic monomers and second their polymerization into conjugated polymers.

In the present paper, we succeeded in the simple radiation induced oxidative polymerization of EDOT and in the synthesis of PEDOT polymers in DCM under N₂ atmosphere. For all irradiation doses, oligomers with several EDOT units were observed. Some polymers with higher molecular weight up to 20 EDOT units were also detected from 36 kGy. Also, whatever the irradiation dose, the polymers were found naturally doped with chloride anions generated in the medium through dichloromethane radiolysis. As demonstrated by UV-vis absorption spectrophotometry, ATR-FTIR spectroscopy and SEC chromatography, the dose of 36 kGy is the optimal irradiation dose which enables quantitative polymerization of 10 mM in EDOT and as a consequence, the yield of EDOT oxidation in DCM, under N₂ atmosphere, amounts to 4.12×10^{-7} mol.J⁻¹. Above this irradiation dose, an overoxidation is systematically observed, which leads to degradation of PEDOT polymer chains.

The morphology of PEDOT polymers radiosynthesized at an irradiation dose of 36 kGy was checked in DCM solution and after deposition. The observations and characterizations made by cryo-TEM, SEM and AFM microscopies, by XRD analysis, EDX spectroscopy and AFM-IR nanospectroscopy demonstrated that radiolysis of DCM leads to the production of amorphous PEDOT polymers doped with chloride ions and highlighted the self-assembly of these polymers into polydisperse globular particles (size comprised between 100 nm and 1.5 μm). Besides, physico-chemical and electrochemical performances of PEDOT polymers radiosynthesized at an irradiation dose of 36 kGy were evaluated by thermogravimetric analysis, cyclic voltammetry and four-point probe technique. PEDOT polymers synthesized by the original radiolytic method were found to be characterized by good thermal stability and by interesting electronic properties (band gap and conductivity), which are comparable to those reported in literature for PEDOT polymers synthesized by chemical or electrochemical methodologies. Our radiation chemistry-based methodology definitely appears as a promising method for the production, not only in water but also in organic solvents, of usable conducting polymers for practical applications.

Current research aims to develop new synthesis strategies and new conducting polymers with tuned morphologies and optimized properties. The present results encourage us to investigate the radiation induced polymerization of other conducting polymers, such as poly(3-hexylthiophene) (P3HT, the monomers of which are insoluble in water) or some other polythiophene derivatives in DCM solvent as well as in other alternative organic solvents (chloroform, cyclohexane...). Also, pulsed radiolysis studies coupled with structural and spectroscopic characterizations are underway to identify the first steps of the polymerization mechanism and to better understand the growth process of conducting polymers in organic solvents. Besides, synthesis of nanostructured conjugated polymers having neat nanostructure with longer polymer chains is foreseeable to get optimized electrical properties. In this context, synthesis of conducting polymers in microemulsions by the way of gamma-rays is under investigation. It should lead to the production of nanostructured conducting polymers either in the water phase or in the hydrophobic phase. Moreover, synthesis of copolymers or mixtures of conducting polymers will also be considered in such microemulsions.

More generally, radiation induced synthesis of conducting polymers could interestingly be considered into soft or hard templates and even into complex matrices since gamma-radiations are characterized by strong penetrating power and are known to lead to very homogeneous processes. This evidently gives us a glimpse of future promising applications.

Author information

*Corresponding author. E-mail: samy.remita@u-psud.fr. Tel.: +33 (0)1 69 15 44 41.

Acknowledgments

We thank Fabrice Goubard and Pierre-Henri Aubert (LPPI, Université de Cergy-Pontoise, France) for conductivity measurements. Also, we thank Romuald Saint-Martin (ICMMO, Université Paris-Sud, France) for XRD analysis and Jean-Michel Guigner (IMPMC, Université Pierre et Marie Curie, France) for Cryo-TEM experiments.

References

1. T. A. Skotheim and J. Reynolds, *CRC Press*, 2007, **3rd edn.**
2. A. J. Heeger, *J. Phys. Chem. B*, 2001, **105**, 8476-8491.
3. C. K. Chiang, S. C. Gau, C. R. Fincher Jr, Y. W. Park, A. G. MacDiarmid and A. J. Heeger, *Appl. Phys. Lett.*, 1978, **33**, 18-20.
4. K. Tremel and S. Ludwigs, *Adv. Polym. Sci.*, 2014, **265**, 39-82.
5. L. A. P. Kane-Maguire and G. G. Wallace, *Chem. Soc. Rev.*, 2010, **39**, 2545-2576.
6. H. Ohkita and S. Ito, *Polym. J.*, 2011, **52**, 4397-4417.
7. A. K. Wanekaya, M. A. Bangar, M. Yun, W. Chen, N. V. Myung and A. Mulchandani, *J. Phys. Chem. C*, 2007, **111**, 5218-5221.
8. A. Mishra, C. Q. Ma and P. Bäuerle, *Chem. Rev.*, 2009, **109**, 1141-1276.
9. E. Pardieu, H. Cheap, C. Vedrine, M. Lazerges, Y. Lattach, F. Garnier, S. Remita and C. Pernelle, *Anal. Chim. Acta*, 2009, **649**, 236-245.
10. C. Q. Jiang, G. M. Chen and X. Wang, *Synth. Met.*, 2012, **162**, 1968-1971.
11. R. Sugimoto, S. Takeda, H. B. Gu and K. Yoshino, *Chem. Express*, 1986, **1**, 635-638.
12. J. Roncali, *Chem. Rev.*, 1992, **92**, 711-738.
13. Y. Lattach, N. Fourati, C. Zerrouki, J. M. Fournion, F. Garnier, C. Pernelle and S. Remita, *Electrochim. Acta*, 2012, **73**, 36-44.
14. J. Ruiz, B. Gonzalo, J. R. Dios, J. M. Laza, J. L. Vilas and L. M. León, *Adv. Polym. Tech.*, 2013, **32**, E180-E188.
15. Y. Lattach, A. Deniset-Besseau, J. M. Guigner and S. Remita, *Radiat. Phys. Chem*, 2013, **82**, 44-53.
16. Y. Lattach, C. Coletta, S. Ghosh and S. Remita, *Chemphyschem*, 2014, **15**, 208-218.
17. Z. Cui, C. Coletta, A. Dazzi, P. Lefrancois, M. Gervais, S. Neron and S. Remita, *Langmuir*, 2014, **30**, 14086-14094.
18. Z. Cui, C. Coletta, R. Rebois, S. Baiz, M. Gervais, F. Goubard, P. H. Aubert, A. Dazzi and S. Remita, *Radiat. Phys. Chem*, 2016, **119**, 157-166.
19. C. Coletta, Z. Cui, A. Dazzi, J. M. Guigner, S. Neron, J. L. Marignier and S. Remita, *Radiat. Phys. Chem*, 2016, **126**, 21-31.
20. C. Coletta, Z. Cui, P. Archirel, P. Pernot, J. L. Marignier and S. Remita, *J. Phys. Chem. B*, 2015, **119**, 5282-5298.
21. S. S. Emmi, G. Poggi, M. D'Angelantonio, M. Russo and L. Favaretto, *Radiat. Phys. Chem*, 2003, **67**, 251-256.
22. T. H. Chen, K. Y. Wong and F. J. Johnston, *J. Phys. Chem.*, 1960, **64**, 1023-1025.
23. S. S. Emmi, G. Beggiato and G. Casalboremiceli, *Radiat. Phys. Chem*, 1989, **33**, 29-37.
24. Z. B. Alfassi, S. Mosseri and P. Neta, *J. Phys. Chem.*, 1989, **93**, 1380-1385.
25. A. Ishigaki and H. Koizumi, *Radiat. Phys. Chem*, 2012, **81**, 803-806.
26. S. S. Emmi, M. D'Angelantonio, G. Beggiato, G. Poggi, A. Geri, D. Pietropaolo and G. Zotti, *Radiat. Phys. Chem*, 1999, **54**, 263-270.
27. A. A. Isse, C. Y. Lin, M. L. Coote and A. Gennaro, *J. Phys. Chem. B*, 2011, **115**, 678-684.
28. K. Ushida, Y. Yoshida, T. Kozawa, S. Tagawa and A. Kira, *J. Phys. Chem. A*, 1999, **103**, 4680-4689.
29. Y. Lattach, P. Archirel and S. Remita, *J. Phys. Chem. B*, 2012, **116**, 1467-1481.
30. E. J. Beiting, K. J. Zeringue and R. E. Stickel, *Spectrochim. Acta A*, 1985, **41**, 1413-1418.
31. S. Truszkowski and W. Szymański, *J. Radioanal. Nucl. Chem*, 1994, **177**, 415-423.
32. T. Nie, K. X. Zhang, J. K. Xu, L. M. Lu and L. Bai, *J. Electroanal. Chem*, 2014, **717**, 1-9.
33. D. Hohnholz, A. G. MacDiarmid, D. M. Sarno and W. E. Jones, *ChemComm*, 2001, 2444-2445.
34. T. Kim, J. Kim, Y. Kim, T. Lee, W. Kim and K. S. Suh, *Curr. Appl. Phys.*, 2009, **9**, 120-125.
35. J. Jang, M. Chang and H. Yoon, *Adv. Mater.*, 2005, **17**, 1616-+.

36. S. Ghosh, H. Remita, L. Ramos, A. Dazzi, A. Deniset-Besseau, P. Beaunier, F. Goubard, P. H. Aubert, F. Brisset and S. Remita, *New J. Chem*, 2014, **38**, 1106-1115.
37. H. Behniafar and D. Yousefzadeh, *Designed Monomers and Polymers*, 2015, **18**, 6-11.
38. H. B. Zhou, G. Y. Han, Y. Z. Chang, D. Y. Fu and Y. M. Xiao, *J. Power Sources*, 2015, **274**, 229-236.
39. J. W. Choi, M. G. Han, S. Y. Kim, S. G. Oh and S. S. Im, *Synth. Met.*, 2004, **141**, 293-299.
40. Y. Hui, C. Bian, J. F. Wang, J. H. Tong and S. H. Xia, *Sensors*, 2017, **17**.
41. W. Feng, Y. Li, J. Wu, H. Noda, A. Fujii, M. Ozaki and K. Yoshino, *J. Phys. Condens. Matter*, 2007, **19**.
42. B. Gupta, M. Mehta, A. Melvin, R. Kamalakannan, S. Dash, M. Kamruddin and A. K. Tyagi, *Mater. Chem. Phys.*, 2014, **147**, 867-877.
43. Q. Zhao, R. Jamal, L. Zhang, M. C. Wang and T. Abdiryim, *Nanoscale Res. Lett.*, 2014, **9**.
44. J. Pommerehne, H. Vestweber, W. Guss, R. F. Mahrt, H. Bassler, M. Porsch and J. Daub, *Adv. Mater.*, 1995, **7**, 551-554.
45. A. A. Farah, S. A. Rutledge, A. Schaarschmidt, R. Lai, J. P. Freedman and A. S. Helmy, *J. Appl. Phys.*, 2012, **112**.
46. B. H. Jones, K. Y. Cheng, R. J. Holmes and T. P. Lodge, *Macromolecules*, 2012, **45**, 599-601.

We originally used radiation chemistry as an alternative methodology for synthesizing conducting polymers in an organic solvent.

